

# 1 LOW TEMPERATURE REGENERATION OF ACTIVATED CARBONS USING 2 MICROWAVES: REVISING CONVENTIONAL WISDOM

3 E. Çalışkan<sup>1,2</sup>, J.M. Bermudez<sup>3</sup>, J.B. Parra<sup>3</sup>, J.A. Menéndez<sup>3</sup>, M. Mahramanlioğlu<sup>4</sup>, C.O. Ania<sup>3\*</sup>

4 <sup>1</sup> Marmara University, Dpt. Basic Pharmaceutical Sciences, 34668, Haydarpasa, Istanbul, Turkey

5 <sup>2</sup> Istanbul University, Institute of Sciences, Chemistry Department, 34116 Vezneciler, Istanbul,  
6 Turkey

7 <sup>3</sup> Instituto Nacional del Carbon (INCAR, CSIC) 33011 Oviedo, Spain

8 <sup>4</sup> Istanbul University, Engineering Faculty, Chemistry Dept. 34320, Avcilar, Istanbul, Turkey

9 \*Corresponding author E-mail: [conchi.ania@incarcsic.es](mailto:conchi.ania@incarcsic.es)

## 10 Abstract

11 The purpose of this work was to explore the application of microwaves for the low  
12 temperature regeneration of activated carbons saturated with a pharmaceutical compound  
13 (promethazine). Contrary to expectations, microwave-assisted regeneration did not lead to  
14 better results than those obtained under conventional electric heating. At low temperatures  
15 the regeneration was incomplete either under microwave and conventional heating, being  
16 this attributed to the insufficient input energy. At mild temperatures, a fall in the adsorption  
17 capacity upon cycling was obtained in both devices, although this was much more  
18 pronounced for the microwave. These results contrast with previous studies on the benefits  
19 of microwaves for the regeneration of carbon materials. The fall in the adsorption capacity  
20 after regeneration was due to the thermal cracking of the adsorbed molecules inside the  
21 carbon porous network, although this effect applies to both devices. When microwaves are  
22 used, along with the thermal heating of the carbon bed, a fraction of the microwave energy  
23 seemed to be directly used in the decomposition of promethazine through the excitation of  
24 the molecular bonds by microwaves (microwave-lysis). These results point out the nature  
25 of the adsorbate and its ability to interact with microwave are key factors that control the  
26 application of microwaves for regeneration of exhausted activated carbons.

27 Keywords: microwave; regeneration; pharmaceuticals; activated carbon; microwave-lysis

28

## 1 1. INTRODUCTION

2 Industrial applications of microwave technology were initiated after the commercialization  
3 of domestic ovens, and since then it has been used in many fields (food processing, drying  
4 processes, polymerization of resins and polymers), most of them based on the ability of  
5 microwaves to heat substances (Jones *et al.*, 2002; Meredith, 1998). From a technological  
6 point of view, microwaves offer a number of advantages over conventional electric heating  
7 such as rapid and selective material heating, quick start-up and stopping, and high level of  
8 safety and automatization. Additionally, the microwave heating of a dielectric material is a  
9 volumetric heating that occurs from the interior of the material.

10 Microwave heating occurs through the interaction of the electric field component of the  
11 microwaves with a) the dipoles (permanent or induced) or b) the charged particles present  
12 in some materials. In this regard, carbon materials are good microwave absorbers as a  
13 consequence of the interactions of the delocalized  $\pi$ -electrons with the microwaves, thus  
14 converting microwave energy into heat. For this reason, the combination of carbon  
15 materials and microwave heating has been widely explored in many fields covering soil  
16 remediation processes, pyrolysis of biomass and organic wastes, and regeneration of  
17 exhausted carbon beds (Menéndez *et al.*, 2010).

18 A number of studies in the literature including our own previous work have reported the  
19 use of microwaves for the thermal regeneration of activated carbons (AC) saturated with  
20 different pollutants (Ania *et al.*, 2004, 2005, 2007; Bo *et al.*, 2008; Cha *et al.*, 2004; Chang  
21 *et al.*, 2010; Emamipur *et al.*, 2007; Fang and Lai, 1996; Hashisho *et al.*, 2005; Kim and  
22 Ahn, 2008; Kuo, 2008; Liu *et al.*, 2007; Price and Schmidt, 1997; Robers *et al.*, 2005; Tai  
23 and Lee, 2007; Wang *et al.*, 2010; Yuen and Hameed, 2009; Robinson *et al.*, 2008; Jou,  
24 2006; ). All of them report the supremacy of microwave-assisted regeneration of AC at  
25 high temperatures over conventional heating for a number of reasons: fast heating,  
26 economic savings due to shorter exposure times, and a superior regeneration efficiency  
27 over a larger number of cycles. Furthermore, microwave technology allowed the activated  
28 carbons to be recycled and reused several times. And it was shown that the use of this  
29 technique causes no damage to the carbon, preserving the porous structure of the

1 regenerated carbons; rather, an increased in the surface area can be achieved during the first  
2 regeneration cycles (Ania *et al.*, 2005, 2007).

3 On the other hand, although low temperature regeneration under conventional heating has  
4 been investigated by some authors (Cabal *et al.*, 2009; Zhu, 2009), it is still not clear  
5 whether this method offers clear advantages over conventional ones (beyond a reduction in  
6 the energy penalty). Therefore the main objective of this study was to explore the  
7 application of microwave-assisted treatment to the regeneration of AC saturated with a  
8 pharmaceutical compound (i.e., promethazine). The efficiency of the low temperature  
9 regeneration process and its impact on the characteristics of the adsorbent as well as on its  
10 adsorptive performance along subsequent cycles was carefully investigated. The results  
11 were compared with those of thermal reactivation conducted under conventional electric  
12 heating in similar operating conditions. Our results show that microwave assisted  
13 regeneration of exhausted carbon beds may present outstanding disadvantages over  
14 conventional heating. The anomalous underperformance of microwave regeneration is  
15 herein reported for the first time, and discussed in terms of the nature of the target pollutant.

16

## 17 **2. MATERIALS AND METHODS**

### 18 **2.1. Materials**

19 Powdered activated carbon (carbon A) supplied by Norit was chosen for this study. The  
20 chemical composition of the carbon is shown in Table S1. Promethazine hydrochloride  
21 (PMET) of 98% purity was supplied by Sigma-Aldrich (Spain). All the promethazine  
22 solutions were prepared in distilled water without pH adjustment. For the purpose of  
23 clarity, the structural formula of PMET is shown in the Supplementary File (Figure S1).

### 24 **2.2 Regeneration of the saturated activated carbon**

25 Prior to the regeneration studies, the AC was saturated with the pharmaceutical compound  
26 in batch experiments using an excess of PMET solution (i.e., 10 g L<sup>-1</sup>) and kept under  
27 stirring for 48 h. The saturated sample (AX) was filtered and dried at 100 °C for 2 h before  
28 regeneration. The procedure and the characteristics of the microwave and electric furnaces

1 used have been described elsewhere (Ania *et al.*, 2005; Fidalgo *et al.*, 2008). For each  
2 regeneration, about 10 g of the dried saturated carbon were placed in a quartz reactor and  
3 purged with N<sub>2</sub> (60 ml min<sup>-1</sup>). The inert atmosphere was maintained during the heating-up  
4 and cooling-down intervals. Regeneration was carried out at different temperatures between  
5 300-500 °C varying the exposure times (5, 15, 30, 60 min). For regeneration in the  
6 microwave device (MW), the time needed to reach the selected temperature was very fast  
7 (ca. 5-7 min). This was not the case in the conventional electric furnace (EF). Therefore, in  
8 order to minimize the differences between the operating conditions of both systems, the  
9 electric device was preheated at 100 °C and the heating rate was adjusted to the maximum  
10 output value, which enabled the target temperature to be reached in 11 min. The samples  
11 after regeneration will be denoted as AX (saturated carbon) followed by a reference to the  
12 furnace (W and E for microwave and electric furnace, respectively), temperature and time  
13 (e.g., AXW300-20 for the sample regenerated in the microwave furnace at 300 °C for 20  
14 minutes). Any likely modifications of the physicochemical features of the AC as a  
15 consequence of the thermal treatment itself were evaluated by performing blank  
16 experiments, which will be denoted as A followed by the reference to the device,  
17 temperature and time (e.g., AW300-15).

### 18 **2.3 Textural and chemical characterization**

19 Textural characterization was carried out by measuring the N<sub>2</sub> adsorption isotherms at  
20 -196 °C in an automatic apparatus (Tristar 3000, Micromeritics). Before the experiments,  
21 the samples were outgassed under vacuum at 120 °C overnight. The isotherms were used to  
22 calculate the specific surface area S<sub>BET</sub>, total pore volume V<sub>T</sub>, and pore size distribution  
23 using the density functional theory method (Rouquerol *et al.*, 1999). The as-received,  
24 saturated and reactivated samples were further characterized by the point of zero charge  
25 (Noh and Schwarz, 1989) and thermal analysis. The thermal analyzer (Labsys, Setaram)  
26 was set to operate at a heating rate 15 °C min<sup>-1</sup> under a nitrogen flow rate of 100 ml min<sup>-1</sup>.  
27 For each measurement about 25 mg of carbon sample was used.


28

29

### 1 3. RESULTS AND DISCUSSION

#### 2 3.1 Promethazine adsorption on the activated carbon

3 The saturated carbon (AX) was initially characterized in a thermobalance (Figure 1 A), to  
 4 investigate the adsorbate-adsorbent interactions and their dependence on temperature. The  
 5 profiles revealed three desorption peaks centered at around 100, 250 and 500 °C.

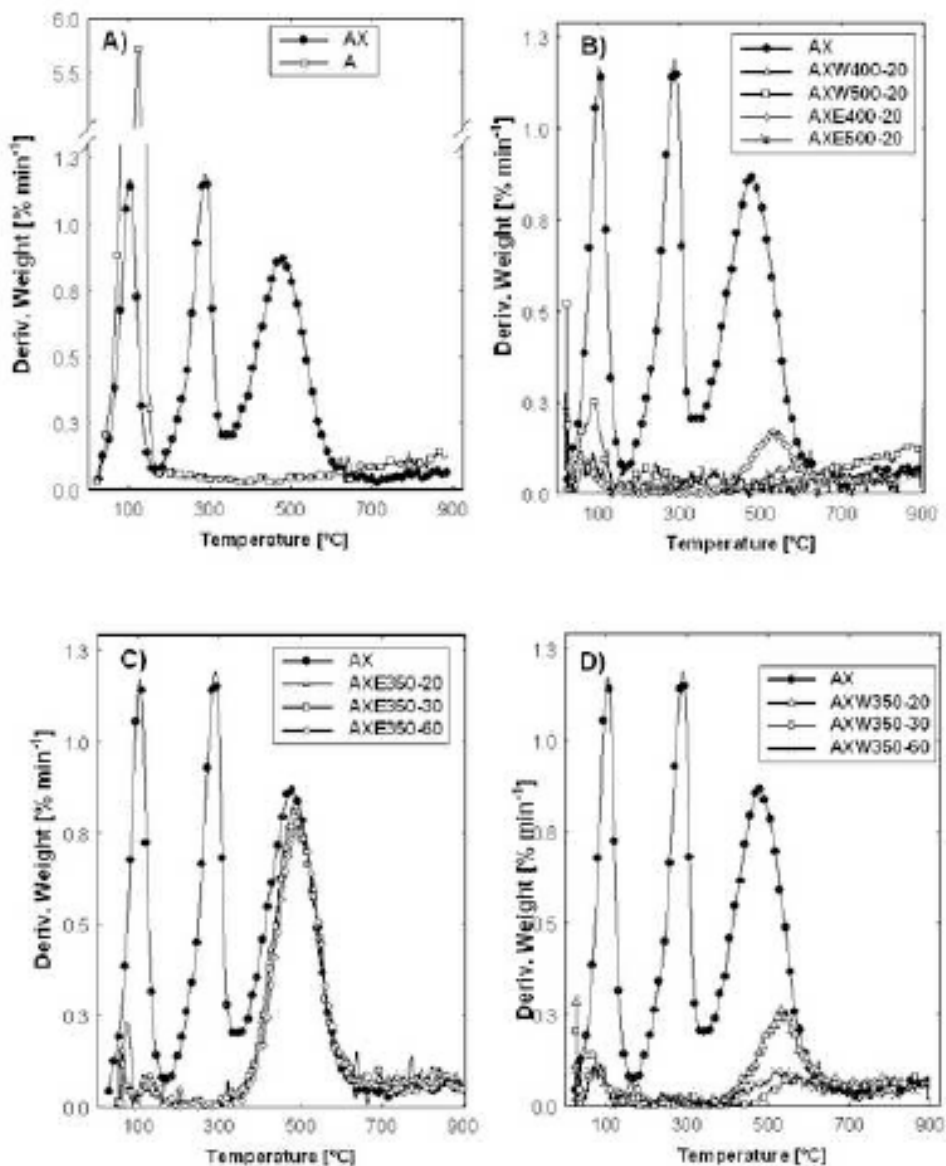

6

7 **Figure 1.** Desorption profiles of the initial and saturated activated carbon (A) subjected to  
 8 regeneration under various conditions: B) 400 and 500 °C in EF and MW; C) 350 °C in EF;  
 9 D) 350 °C in MW.

1 The first peak was assigned to the moisture present in the AC. Subsequent peaks were only  
2 observed for the saturated carbon, and they were attributed to interactions between the  
3 pharmaceutical compound and the carbon surface in different sites of adsorption. The peak  
4 centered at about 270 °C was assigned to the desorption of PMET retained in the low  
5 energy adsorption sites in the AC (physisorption), whereas the second peak at higher  
6 temperature was attributed to the evolution of the chemisorbed compound. Indeed,  
7 calculation of the activation energies of the two peaks from the profiles at different heating  
8 rates rendered 48 and 155 kJ mol<sup>-1</sup>, respectively. Analogous desorption profiles showing  
9 several peaks have been reported for other aromatic compounds on AC (Cabal *et al.*, 2009).

10 On the basis of the thermogravimetric profiles of the saturated carbon, it seems reasonable  
11 to assume that the regeneration temperature has to be a priori high enough to promote the  
12 evolution of both the physisorbed and the chemisorbed fractions (between 250 and 650 °C).  
13 Indeed preliminary studies indicated that temperatures below 300 °C were too low (data  
14 non shown), with a small desorption of the physisorbed fraction of PMET even after  
15 prolonged regeneration times. Since our objective was to explore the low temperature  
16 regeneration process, temperatures between 300 and 500 °C were chosen for both the  
17 microwave and the electric furnaces.

### 18 **3.2 Low temperature regeneration of the saturated carbon**

19 Blank experiments were conducted at temperatures between 300-500 °C to evaluate the  
20 effect of the thermal treatment itself on the adsorbent. Tables 1 and S1 show that other than  
21 a slight fall in the oxygen content, the textural and the chemical properties of the AC  
22 remained unchanged due to the thermal treatment. Indeed, because of the hydrophobic  
23 character of the carbon and the low temperatures applied, no structural annealing was  
24 expected (Rao *et al.*, 1996).

25 During the regeneration, desorption of PMET or its decomposition intermediates occurred  
26 between 200-500 °C (change in the colour of the evolved gases). Simultaneously a whitish  
27 precipitate, identified as PMET by infrared analysis, was observed to condense in the cold  
28 parts of the reactor. This also occurred in subsequent regeneration cycles. The extent of  
29 PMET desorption was evaluated by means of thermal analysis of the regenerated samples.

1 **Table 1.** Nanotextural characterization of the exhausted activated carbon (AX) after  
 2 thermal regeneration at various temperatures in the electric (E) and microwave  
 3 (W) furnace.

	$S_{\text{BET}}$ [m <sup>2</sup> g <sup>-1</sup> ]	$V_{\text{TOTAL}}^{\text{a}}$ [cm <sup>3</sup> g <sup>-1</sup> ]	$V_{\text{MICROPORES}}^{\text{b}}$ [cm <sup>3</sup> g <sup>-1</sup> ]	$V_{\text{MESOPORES}}^{\text{b}}$ [cm <sup>3</sup> g <sup>-1</sup> ]
A	1062	0.536	0.329	0.107
AX	250	0.162	0.046	0.051
AW350-60	1060	0.536	0.330	0.106
AW500-60	1065	0.536	0.331	0.106
AE350-60	1070	0.540	0.333	0.105
AE500-60	1095	0.550	0.340	0.107
AXW350-20	823	0.457	0.232	0.119
AXW350-30	709	0.390	0.194	0.111
AXW350-60	661	0.360	0.187	0.096
AXE350-20	534	0.307	0.094	0.085
AXE350-30	661	0.362	0.121	0.103
AXE350-60	665	0.360	0.119	0.107
AXW500-C1	578	0.325	0.163	0.101
AXW500-C3	610	0.335	0.104	0.087
AXW500-C5	591	0.338	0.104	0.040
AXE500-C1	717	0.384	0.203	0.111
AXE500-C3	757	0.395	0.217	0.105
AXE500-C5	860	0.480	0.242	0.130

<sup>a</sup> evaluated at relative pressure 0.99


<sup>b</sup> evaluated by DFT method applied to nitrogen adsorption data

4  
 5  
 6 Figure 1 (plots B,C,D) shows the differential thermogravimetric profiles (DTG) of the  
 7 saturated carbon subjected to regeneration at different temperatures in both devices. The  
 8 peak assigned to chemisorbed PMET (i.e., centered at 500 °C) was still detected in the DTG  
 9 profiles after regeneration at 350 °C in both devices, indicating that desorption was  
 10 incomplete under these conditions. However, at 350 °C the amount desorbed was much  
 11 larger when the carbon was heated in the MW. Whereas regeneration in the EF at 350 °C  
 12 only provoked the desorption of the physisorbed PMET (as expected bearing in mind the  
 13 regeneration temperature), microwave heating induced the removal of the physi- and

1 chemisorbed PMET fraction. In other words, microwave heating seemed to be more  
2 powerful than heating in a conventional furnace. PMET was almost totally desorbed by  
3 heating at 350 °C in the microwave (ca. mass loss below 1 wt.%), even though the applied  
4 temperature was lower than that corresponding to the chemisorbed fraction (Figure 1 A).

5 When the treatment was carried out in the electric furnace at 350 °C, the DTG profiles  
6 show that the amount of PMET that remained inside the AC was very large (even for  
7 prolonged times). Therefore, the experiments were conducted at higher temperatures. It  
8 appeared that the temperature needed to be raised to 500 °C to achieve the complete  
9 desorption of PMET under conventional heating. The DTG profiles in the MW and the EF  
10 at 500 °C were rather close (Figure 1B), evidencing that the differences between both  
11 devices become smaller at high temperatures. The results shown that better desorption  
12 yields are obtained for microwave-assisted heating when low temperatures are used.

13 The influence of thermal regeneration on the subsequent adsorption capacity of PMET was  
14 investigated at various temperatures and after successive regeneration cycles (Figures 2 and  
15 S2). For the sake of comparison, the adsorption capacities of the AC exposed to thermal  
16 heating (blanks) have also been included. It can be seen that the adsorption capacity of the  
17 raw carbon did not change much when it was exposed to moderate temperatures in the MW  
18 and EF (series AW and AE). This was somehow expected since the thermal treatment itself  
19 did not substantially modify its porous structure or composition (Tables 1 and S1).

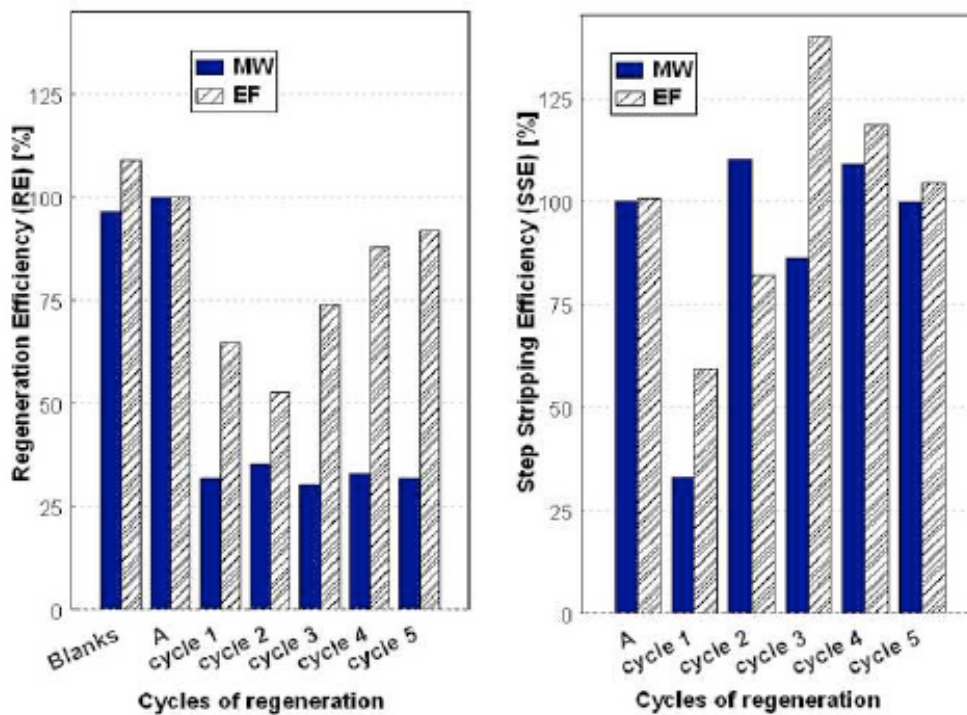

**Figure 2.** Regeneration Efficiency (RE) and Step Stripping Efficiency (SSE) upon regeneration at 500 °C in the electric furnace (EF) and the microwave (MW).

Upon regeneration at 350 °C the PMET adsorption capacity of the carbon decreased drastically for both series treated in the MW and the EF (Figure S2). The DTG profiles (Figure 1C) indicate that this behavior could be due to an incomplete desorption of PMET molecules, assuming that 350 °C would be too low to promote the desorption of the physi- and chemisorbed fractions of PMET. This hypothesis may be valid for regeneration in the EF (as confirmed by Figure 1C), but not for the MW. A sharp decrease in PMET adsorption capacity was also observed after microwave-assisted regeneration at 350 °C, which contrasts with the low mass loss of the DTG profiles of the corresponding samples (Figure 1D) that had suggested that PMET is completely desorbed under these conditions. Moreover, when the temperature is raised to 400 and 500 °C, the fall in the adsorption capacity is still remarkable, but it becomes more pronounced for the sample regenerated in the MW. Indeed, it seems that the better performance of the AC (in terms of PMET retention) after regeneration in the MW compared to EF is only valid for low temperatures, whereas the opposite trend applies from 400 °C.

1 Our results contrast with previous studies reporting a more efficient regeneration of  
2 saturated AC when MW heating is applied (Ania *et al.*, 2004, 2005, 2007; Chang *et al.*,  
3 2010; Hashisho *et al.*, 2005; Kuo, 2008; Liu *et al.*, 2007; Price and Schmidt, 1997; Tai *et*  
4 *al.*, 2007; Wang *et al.*, 2010; Yuen and Hameed, 2009). In fact, a literature survey of the  
5 studies available in the bibliography on the use of microwaves for the regeneration of  
6 carbon materials saturated with organic pollutants shows that all of them reported the  
7 benefits of MW-assisted heating, particularly when compared to conventional heating. A  
8 summary of available data found in the literature (including our previous works) is  
9 compiled in Table 2. Consequently, conventional wisdom on this topic supports the  
10 supremacy of microwave over conventional electric heating as a general rule.

11 To further comprehend the herein tendency obtained for low and mild temperature  
12 regeneration, we have analyzed the process considering different viewpoints that  
13 encompass not only the heating mechanism (MW vs EF) but also the characteristics of the  
14 system (adsorbent –adsorbate).

15 On the basis of the thermogravimetric analysis (Figure 1), it seems reasonable to assume  
16 that the deterioration of the adsorption capacity of the regenerated samples could be linked  
17 to the thermal cracking of the adsorbed PMET molecules inside the carbon material during  
18 the regeneration step. The decomposition products would cause a pore plugging effect on  
19 the adsorbent, preventing the carbon porosity from being reused in subsequent adsorption  
20 cycles. This hypothesis is widely found in the literature to explain the decrease (whether  
21 low or high) in the adsorption capacity of regenerated carbons, regardless of the heating  
22 mechanism (Ania *et al.*, 2004, 2005, 2007; Cabal *et al.*, 2009; Chang *et al.*, 2010; Hashisho  
23 *et al.*, 2005; Kuo, 2008; Liu *et al.*, 2007; Price and Schmidt, 1997; Wang *et al.*, 2010; Yuen  
24 and Hameed, 2009). However the thermal decomposition of PMET would be expected to  
25 occur in both the EF and the MW, and our results suggest that the thermal cracking of this  
26 compound is accelerated under microwave irradiation, underlying the importance of the  
27 nature of the adsorbate.

28

29

1 **Table 2.** Summary of previous studies on the regeneration of carbonaceous materials using  
 2 microwave technology. Data of available publications according to ISI Web of  
 3 Knowledge, 20/12/2010. Search terms: (a) “microwave AND regeneration AND  
 4 carbon”, (b) “carbon AND regeneration AND microwave\*”.

Compound	Reference	Remarks
Ethanol, acetone	Fang, 1996	Low carbon losses upon MW irradiation of the saturated carbon; adsorption capacity is maintained upon 3 cycles.
5-chlorophenol	Price, 1997	High level of adsorption capacity after several cycles
Phenol	Ania, 2004	MW outperforms conventional regeneration
Phenol	Ania, 2005	MW outperforms conventional regeneration
Salicylic acid	Ania, 2007	MW outperforms conventional regeneration
Toluene, ethyl acetate, methylene chloride	Cha, 2004	MW restored the original adsorption capacity
Methy-ethyl-ketone	Emamipour, 2007	Dynamic desorption tests; good performance of a microwave swing adsorption system
PAH, VOCs,	Hashisho, 2005	Rapid regeneration; adsorption capacity is maintained after 3 cycles
Acid Orange	Bo, 2008	Initial adsorption capacity was maintained after 2 cycles
Benzene	Kim, 2008	Initial adsorption capacity maintained after 5 cycles
Reactive Red	Kuo, 2008	MW regeneration outperformed NaOH extraction
Reactive Black 5	Chang, 2010	Adsorption capacity is maintained over 7 cycles
2,4,5-trichlorobiphenyl	Liu, 2007	Adsorption capacity maintained high level after five adsorption/regeneration cycles.
Methy-ethyl-ketone	Tai, 2007	MW-induced regeneration restored initial capacity
Dye Reactive Red 3BS	Wang, 2010	High regeneration efficiencies achieved after several cycles; fall in adsorption capacity due to thermal cracking under MW
Acid Orange 7	Yuen, 2009	Initial adsorption capacity and rate maintained at high a level over several cycles. The damage to carbon upon MW irradiation was lower than for conventional regeneration methods.
Triethylamine, acetic acid	Robers, 2005	Best results obtained with MW and ultrasonic–water regeneration
n-alkanes (C <sub>12</sub> –C <sub>20</sub> )	Robinson, 2008	Technological and energetic advantages of MW-assisted over conventional gas stripping operations are reported in the removal of oils from contaminated drill cuttings.
Pb (II)	Jou, 2006	MW allows the immobilization of heavy metal ions in contaminated soil wastes.

5  
 6 Promethazine is a polar compound that would so be expected to easily absorb microwaves.  
 7 Thus, it might occur that along with the heating of the AC (which is a good microwave

1 absorber), a fraction of the microwave energy supplied is being absorbed by the PMET  
2 molecules retained in the carbon. The heating mechanism using microwave irradiation is  
3 based on a quick molecular level heating. Therefore, the interactions between microwaves  
4 and the chemical bonds of the PMET molecules may eventually facilitate the quick thermal  
5 cracking of the compound (microwave-lysis), and consequently favor the formation of coke  
6 deposits that would block the microporosity of the regenerated adsorbent. The ability of  
7 microwaves to break down a given compound would depend on its chemical nature and  
8 could be governed by its polarity, polarizability, stability, aromaticity, and so forth.

9 For instance, previous works on the regeneration of AC saturated with two aromatic  
10 compounds (phenol and salicylic acid) revealed different behaviors in each case. Salicylic  
11 acid is strongly resistant to thermal cracking (both in MW and EF) due to its ability to  
12 sublimate at 300 °C. In contrast, phenol easily undergoes thermal breakdown when it is  
13 heated at high temperatures, although no enhancement is observed when microwaves are  
14 used maybe due to its high aromatic character (Ania *et al.*, 2004, 2005).

### 16 3.3 Regeneration efficiency over subsequent cycles

17 Successive adsorption-regeneration cycles were performed at 500 °C and the overall  
18 efficiency of the regeneration process was evaluated by means of the regeneration  
19 efficiency (RE) and the single Step Stripping Efficiency (SSE) parameters (Figure 2)  
20 calculated as:

$$21 \text{ RE} = Q_i/Q_o * 100 \text{ (1)}$$

$$22 \text{ SSE} = Q_i/Q_{i-1} * 100, Q_{i-1} \text{ (2)}$$

23 where  $Q_i$  is the adsorptive capacity of the regenerated carbon in a given cycle  $i$ , and  $Q_o$  the  
24 adsorptive capacity of the fresh carbon.

25 The RE gradually decreased after several cycles, this effect being more pronounced after  
26 the first cycle and when regeneration was carried out using microwave heating (i.e., values  
27 below 40% after the first cycle). Comparatively, better results were obtained with  
28 conventional heating. After falling during the first cycle, the RE recovered slightly when

1 the regeneration was conducted in the EF, reaching values above 80% after 4 cycles. In  
2 contrast, the regeneration efficiency of the samples heated in the MW was very poor and  
3 the life span of the AC was dramatically reduced with the number of cycles.

4 The stripping efficiency -SSE- is defined as the ratio between the adsorption capacity of a  
5 given cycle and that of the previous one, and allows the desorption yield in the different  
6 cycles to be evaluated. Unlike RE, the SSE values did not decrease with the number of  
7 cycles with exception of the first one. The gradual increase observed after the second  
8 regeneration cycle, particularly for the samples heated in the conventional furnace, suggests  
9 that the desorption of fresh PMET molecules from the regenerated carbon becomes easier  
10 with the number of cycles. SSE was lower in the MW series, confirming that regeneration  
11 for every cycle is more efficient when conventional heating is used.

12 As previously mentioned, the regeneration time (30 min) was chosen on the basis of  
13 negligible mass loss of the regenerated samples by thermal analysis. However, to determine  
14 whether 30 min was long enough for complete desorption of the retained pollutant, the  
15 saturated carbon was also subjected to a thermal treatment at 500 °C for 60 and 90 min. The  
16 RE values were found to be similar to those after heating for 30 min (i.e., 80, 78 and 77%  
17 for 30, 60 and 90 min, respectively), demonstrating that longer periods of time would only  
18 increase the energy consumption of the process. Similarly, regeneration at 800 °C -the usual  
19 temperature applied in industrial processes- followed the same trend in RE (below 80% in  
20 the first cycle).

### 21 **3.4 Effect of MW regeneration on the textural properties of the activated carbon**

22 Detailed characteristics of the pore structure of the series of as-received, saturated and  
23 regenerated carbons are presented in Table 1). As mentioned above, thermal treatment by  
24 itself (either in MW or EF) did not modify the textural properties and composition of the  
25 carbon. As a general rule, the values of specific surface area and micropore volume of the  
26 raw AC were not restored after regeneration, although the shape of the gas adsorption  
27 isotherms was not changed (data not shown).

28 For the series of carbons treated in the MW at 350 °C, a gradual fall in the porosity of the  
29 regenerated samples was observed with regeneration time. This finding confirms the pore

1 plugging effect mentioned above. Thus, along with the partial desorption of PMET upon  
2 microwave irradiation, the adsorbed molecules could also be irreversibly bound or  
3 degraded inside the AC due to their interaction with the microwaves (microwave-lysis).

4 Comparatively, the blockage of the porosity was greater in the case of the carbon  
5 regenerated at 350 °C in the EF than under microwave heating. This seems reasonable  
6 considering that at this temperature a large fraction of PMET still remained inside the  
7 carbon skeleton (Figure 1C). However, as the regeneration temperature was raised, the  
8 collapse of the porous features become more important for the samples treated in the  
9 microwave.

10 The most pronounced deterioration of the porous features after successive regeneration  
11 cycles corresponded to the regeneration carried out at 500 °C in the microwave, which is in  
12 good agreement with the fall observed in adsorption capacity (Figure S2). The damage to  
13 porosity indicates that the thermal cracking of PMET (and thus pore blockage in the  
14 regenerated samples) became more evident with the rise in temperature. In contrast, when  
15 regeneration was carried out in the EF the porous features of the initial carbon were  
16 somehow recovered with the number of cycles. This would explain the increase in the RE  
17 and SSE parameters after the second and subsequent cycles, pointing to a gradual recovery  
18 of the adsorption capacity of the samples regenerated in the conventional furnace  
19 (Figure S2).

20 In sum, improvement of regeneration efficiency would be expected if the regeneration were  
21 carried out under oxidizing atmosphere (steam, CO<sub>2</sub>, air), which could promote the  
22 activation of the coke deposits formed due to thermal cracking of the adsorbate, thereby  
23 counteracting the pore plugging effect.

#### 24 25 **4. CONCLUSIONS**

26 As a general rule, microwave heating has long been considered a powerful technology for  
27 the regeneration of loaded activated carbons (based on previous works with different  
28 pollutants) due to its superior performance vs conventional heating in terms of regeneration

1 efficiency upon several cycles, adsorption capacities of regenerated samples and economic  
2 savings due to the fast microwave response. The results of this study show that if the nature  
3 of the pollutant is regarded, the use of microwave heating in the regeneration of exhausted  
4 carbons does not guarantee a good performance of the regenerated samples upon cycling.  
5 This has been herein illustrated with the low temperature regeneration of an activated  
6 carbon loaded with a pharmaceutical (promethazine), where microwave-induced  
7 modifications of the pollutant have shown to be determinant in the cycle-ability and  
8 adsorption performance of the regenerated carbon.

9 Incomplete desorption occurred in both devices (EF and MW) when the applied  
10 temperature was too low to promote desorption of the physi- and chemisorbed fractions of  
11 the adsorbed compound (even after long regeneration times). Increasing the regeneration  
12 temperature favored the desorption of the retained compound, although still low  
13 regeneration yields were obtained due to thermal cracking of the adsorbate inside the  
14 porosity of the AC. Contrary to expectations based on previous works carried out on a  
15 variety of pollutants, this effect was more pronounced in the samples regenerated by  
16 microwave irradiation. For this particular compound (promethazine), it seems that  
17 microwave heating leads to a decrease in the efficiency of the regeneration process, due to  
18 an enhanced cracking of the pollutant caused by direct interaction between the adsorbate  
19 and the microwaves (microwave-lysis).

20

## 21 **Acknowledgements**

22 EÇ thanks The Council of Higher Education of Turkey (YÖK) for supporting her stay at  
23 INCAR (Oviedo) and the financial support of Istanbul University Research Fund (Project  
24 3991) for her PhD thesis. JMB acknowledges CSIC for a JAE predoctoral fellowship. COA  
25 thanks the financial support of the projects CTM2008-01956 and CSIC-200980I131.

26

27

28

1 **REFERENCES**

- 2 Ania, C.O., Menendez, J.A., Parra, J.B., Pis, J.J., 2004. Microwave-induced regeneration of  
3 activated carbons polluted with phenol. A comparison with conventional thermal  
4 regeneration. *Carbon* 42, 1377–1381.
- 5 Ania, C.O., Menendez, J.A., Parra, J.B., Pis, J.J., 2005. Effect of microwave and  
6 conventional regeneration on the microporous and mesoporous network and on the  
7 adsorptive capacity of activated carbons. *Microporous Mesoporous Mater.* 85, 7-15.
- 8 Ania, C.O., Menendez, J.A., Parra, J.B., Pis, J.J., 2007. Microwave-assisted regeneration of  
9 activated carbons loaded with pharmaceuticals. *Water Res.* 41, 3299-3306.
- 10 Bo, L.L., Wang, X.C., Lu, L., 2008. Study on the purification and regeneration of activated  
11 carbon by microwave and its adsorption capacity for Acid Orange. *J. Xian Univ. Archit.*  
12 *Technol.* 40, 413-417.
- 13 Cabal, B., Tsyntsarski, B., Budinova, T., Petrov, N., Parra, J.B., Ania, C.O., 2009.  
14 Improved phenol adsorption on carbons after mild temperature steam regeneration. *J.*  
15 *Hazard. Mater.* 166, 1289-1295.
- 16 Cha, C.Y., Wallace, S., George, A.H., Rogers, S., 2004. Microwave Technology for  
17 Treatment of Fume Hood Exhaust. *J. Environ. Eng.* 130, 338-348.
- 18 Chang, S.H., Wang, K.S., Liang, H.H., Chen, H.Y., Li, H.C., Peng, T.H., Su, Y.C., Chang,  
19 C.Y., 2010. Treatment of Reactive Black 5 by combined electrocoagulation–granular  
20 activated carbon adsorption–microwave regeneration process. *J. Hazard. Mater.* 175, 850–  
21 857
- 22 Emamipour, H., Hashisho, Z., Cevallos, D., Rood, M.J., Thurston, D.L., Hay, K.J., Kim,  
23 B.J., Sullivan, P.D., 2007. Steady-State and Dynamic Desorption of Organic Vapor from  
24 Activated Carbon with Electrothermal Swing Adsorption. *Environ. Sci. Technol.* 41, 5063-  
25 5069.
- 26 Fang, C.S., Lai, P.M.C., 1996. Microwave regeneration of spent powder activated carbon,  
27 *Chem. Eng. Commun.* 147, 17-27.
- 28 Fidalgo, B., Dominguez, A., Pis, J.J., Menendez, J.A., 2008. Microwave-assisted dry  
29 reforming of methane. *Int. J. Hydrogen Energy* 33, 4337-4344.

- 1 Hashisho, Z., Rood, M., Botich, L., 2005. Microwave-Swing Adsorption To Capture and  
2 Recover Vapors from Air Streams with Activated Carbon Fiber Cloth. *J. Environ. Sci.*  
3 *Technol.* 39, 6851-6859.
- 4 Jones, D.A., Lelyveld, T.P., Mavrofidis, S.D., Kingman, S.W., Miles, N.J., 2002.  
5 Microwave heating applications in environmental engineering — a review, *Resour.*  
6 *Conserv. Recycl.* 34, 75–90.
- 7 Jou, C.-J.G. 2006. An efficient technology to treat heavy metal-lead-contaminated soil by  
8 microwave radiation, *Journal of Environmental Management*, 78, 1-4.
- 9 Kim, K.J., Ahn, H.G., 2008. A study on adsorption characteristics of benzene over  
10 activated carbons coated with insulating materials and desorption by microwave irradiation.  
11 *J. Korean Ind. Eng. Chem.* 19, 445-451.
- 12 Kuo, C.Y., 2008. Desorption and re-adsorption of carbon nanotubes: Comparison of  
13 sodium hydroxide and microwave irradiation processes. *J. Hazard. Mater.* 152, 949–954.
- 14 Liu, X., Gang, L., Han, W., 2007. Granular activated carbon adsorption and microwave  
15 regeneration for the treatment of 2,4,5-trichlorobiphenyl in simulated soil-washing solution,  
16 *J. Hazard. Mater.* 147, 746–751.
- 17 Menéndez J.A., A. Arenillas, B. Fidalgo, Y. Fernández, L. Zubizarreta, E.G. Calvo, J.M.  
18 Bermúdez, 2010. Microwave heating processes involving carbon materials, *Fuel Processing*  
19 *Technology* 91, 1–8
- 20 Meredith, R., 1998. *Engineers' Handbook of Industrial Microwave Heating*. The Institution  
21 of Electrical Engineers, London, UK.
- 22 Noh, J.S., Schwarz, J.A., 1989. Estimation of the point of zero charge of simple oxides by  
23 mass titration. *J. Colloid Interf. Sci.* 130, 157-164.
- 24 Price, D.W., Schmidt, P.S., 1997. Microwave regeneration of adsorbents at low pressure:  
25 Experimental kinetics studies, *J. Microwave Power EE.* 32, 145-154.
- 26 Rao, A.M., Fung, A.W.P., Dresselhaus, M.S., Endo, M., 1996. Structural characterization  
27 of heat-treated activated carbon fibers. *J. Mater. Res.* 7, 1788-1794.
- 28 Robers, A., Figura, M., Thisen, P.H., 2005. Desorption of odor-active compounds by  
29 microwaves, ultrasound, and water. *AICHe J.* 51, 502-510.

- 1 Robinson, J.P., Kingman, S.W., Onobrakpeya, O. 2008. Microwave-assisted stripping of oil  
2 contaminated drill cuttings, *Journal of Environmental Management*, 88, 211-218.
- 3 Rouquerol, F., Rouquerol, J., Sing, K., 1999. *Adsorption by Powders & Porous Solids*,  
4 Academic Press, London.
- 5 Tai, H.S., Lee, C.H., 2007. Desorption of methy-ethyl-ketone from granular activated  
6 carbon with microwave radiation, *Environ. Prog.* 26, 299-303.
- 7 Wang, J., Peng, X., Luan, Z., Zhao, C., 2010. Regeneration of carbon nanotubes exhausted  
8 with dye Reactive Red 3BS using microwave irradiation. *J. Hazard. Mater.* 178, 1125–  
9 1127.
- 10 Yuen, F.K., Hameed, B.H., 2009. Recent developments in the preparation and regeneration  
11 of activated carbons by microwaves, *Adv. Colloid Interf. Sci.* 149, 19–27
- 12 Zhu, R., Zhu, J., Ge, F., Yuan, P. 2009. Regeneration of spent organoclays after the  
13 sorption of organic pollutants: A review, *Journal of Environmental Management*, 90, 3212-  
14 3216